



John Garner, Manager

PolySciTech Division of
AKINA, INC.
3495 Kent Avenue
West Lafayette, IN 47906
<http://www.polysciotech.com/>
E-mail: jg@akinainc.com

**White-Paper: Acrylate-modified hydrophobicized methylcellulose
(PolyVivo AI147) crosslinking and micro-patterning**

July 11, 2018

Introduction

Photolithography and related photo-crosslinking techniques have come to the forefront lately for use in creating scaffolds or patterns for cell growth and biological interactions [1-3]. Hydrophobicized methylcellulose has already proven itself a viable option for the growth of cells in three-dimensional shapes [4] [5]. A recently generated reagent-version of this material, activated with cross-linkable acrylate groups, has been created and is available from PolySciTech as PolyVivo cat# AI147. This white-paper relates methods for crosslinking this material and steps towards micro-patterning the material using conventional photolithography-based techniques.

Equipment

UVP Blak-Ray™ B-100AP High-Intensity UV Lamp
Olympus BX51 Microscope
AMscope digital camera

Reagents

Acrylate modified hydrophobicized methylcellulose ([PolyVivo Cat# AI147](#), lot# 60901BPR-A)
Deionized water (Sourced from Barnstead™ Easypure™ II)
Ethanol 200 proof (Decon Laboratories, Inc.)
Phosphate buffered saline (Aldrich cat # [P4417](#))
2-Hydroxy-4'-(2-hydroxyethoxy)-2-methylpropiophenone (Irgacure 2959)
(Aldrich cat# [410896](#))


Method

Acrylate modified hydrophobicized methylcellulose (PolyVivo Cat# [AI147](#)) was dissolved in deionized water at 2.5% w/v at 4°C overnight and stored at this temperature prior to use. A 70% v/v solution of ethanol in water was prepared and this solution was used to prepare a 10% w/v solution of photoinitiator (Irgacure 2959) in 70% ethanol. One milliliter of the prepared PolyVivo AI147 2.5% w/v solution was mixed with 0.1 ml of 10% Irgacure 2959 in ethanol and shook gently by hand to mix for a few minutes. This solution was then pipetted onto a PDMS micro-template bearing columns 50 um in diameter x 50 um tall


(prepared as described previously [6-10]) and exposed to UV light at a distance of ~10 cm for 20 minutes to cure. Subsequently, the cured hydrogel was gently pried from the template using flat-bladed tweezers and transferred, upside down, into a small petri dish. The dish was filled to cover over the hydrogel with phosphate buffered saline solution (prepared according to manufacturer instructions) and imaged under a light microscope at 4X and 10X magnification.




A. Mixing of gel-acrylate and photoinitiator

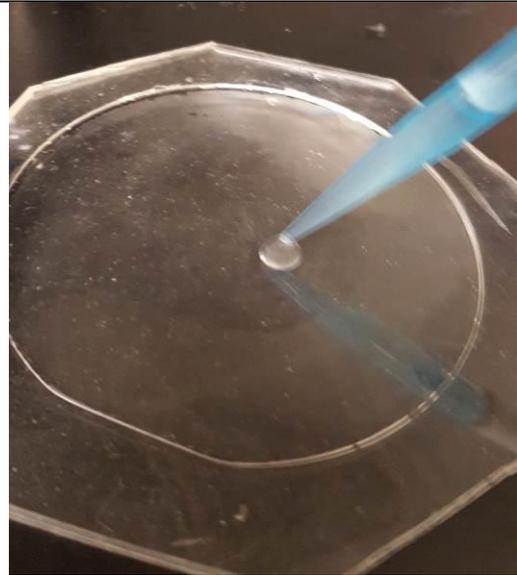

B. Addition to PDMS micro-template

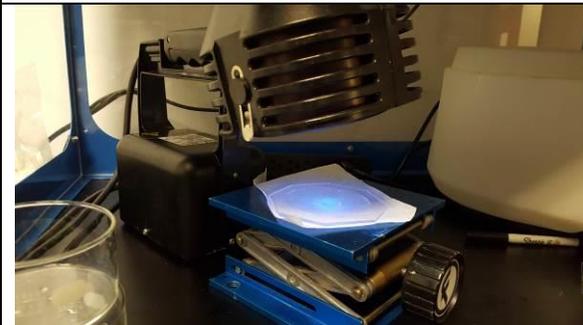

C. UV light exposure.

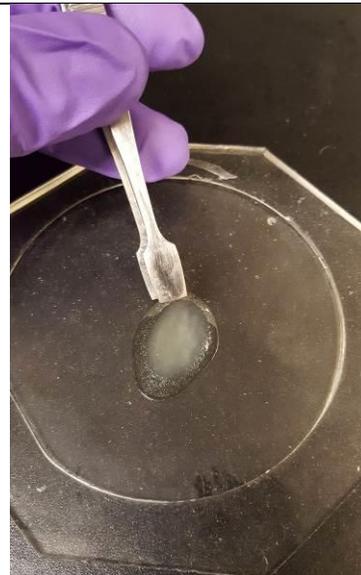

D. Removing cured piece from template



E. Microscope imaging crosslinked gel in saline.

Figure 1. Image series from hydrogel preparation.

Results

The formed hydrogel was observed to not re-dissolve in the room-temperature phosphate buffered saline indicating that it was cross-linked.

Under the microscope, several regions of the hydrogel were observed to have successfully received an imprint of the micro-patterned template (Fig 2) though the pattern form was not completely uniform across the entire surface.

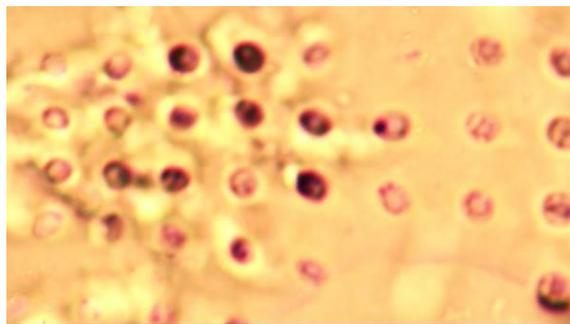


Figure 2. Partial template transfer onto crosslinked hydrogel (10X microscope magnification).

Conclusion

The acrylate-modified HMMC material (PolyVivo AI147) can be used to form photo-crosslinkable gels using conventional photo-reagents, such as Irgacure 2959, and these techniques can be potentially applied to lithography based micro-manufacturing methods. A more concentrated solution than 2.5% w/v of the AI147 is generally suggested to achieve good template transfer for lithography approaches.

References

- [1] J. Garner, K. Park, Chemically modified natural polysaccharides to form gels. *Polysaccharides: Bioactivity and Biotechnology* (2015) 1555-1582.
- [2] J. Garner, K. Park, *GELS HANDBOOK: Fundamentals, Properties and Applications Volume 1: Fundamentals of Hydrogels*, World Scientific, 2016, pp. 17-44.
- [3] F. Ullah, M.B.H. Othman, F. Javed, Z. Ahmad, H.M. Akil, Classification, processing and application of hydrogels: A review. *Materials Science and Engineering: C* 57 (2015) 414-433.
- [4] J.S. Garner, S.M. Skidmore, J.C. Hadar, H. Burnsoo, K. Park, Polymers for Inducing 3D Spheroid Formation of Biological Cells U.S. Patent Application No. 15/533,027., Google Patents, 2017.
- [5] J. Hadar, J. Garner, S. Skidmore, H. Park, K. Park, B. Han, F. Atrian, S.A. Lelièvre., "3DCellMakers: Thermogelling Polymers for 3D Cell Culture" (https://akinainc.com/polyscitech/products/3Dcellmaker/CRS2016_3DCM.pdf). Poster Presentation Controlled Release Society (2016).
- [6] Y. He, K. Park, Effects of the microparticle shape on cellular uptake. *Molecular pharmaceutics* 13(7) (2016) 2164-2171.
- [7] G. Acharya, C.S. Shin, M. McDermott, H. Mishra, H. Park, I.C. Kwon, K. Park, The hydrogel template method for fabrication of homogeneous nano/microparticles. *Journal of Controlled Release* 141(3) (2010) 314-319.
- [8] G. Acharya, M. McDermott, S.J. Shin, H. Park, K. Park, *Biomedical Nanotechnology*, Springer, 2011, pp. 179-185.
- [9] G. Acharya, C.S. Shin, K. Vedantham, M. McDermott, T. Rish, K. Hansen, Y. Fu, K. Park, A study of drug release from homogeneous PLGA microstructures. *Journal of Controlled Release* 146(2) (2010) 201-206.
- [10] Akina, Microparticles
<https://akinainc.com/polyscitech/currentResearch/microparticleFormulation/index.php>.