



No. AK010 Certificate of Analysis

Product Name: Methoxy-Poly(ethylene glycol)-*b*-Poly(D,L-lactide-co-glycolide) copolymer
(M_w 5,000:10,000 Da, 50:50 LA:GA) (Lot#: 60412SJH-B)

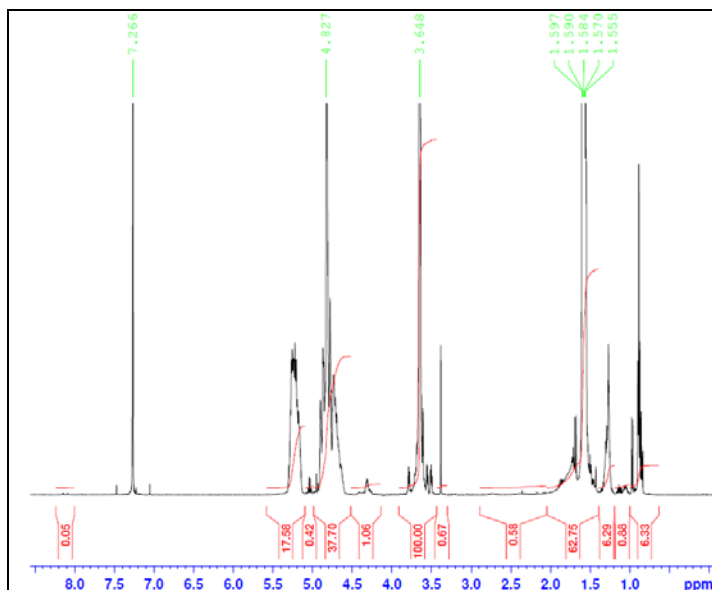


H-NMR spectrum of mPEG-PLGA copolymer in CDCl₃ (Varian Inova 500 MHz instrument), NMR of mPEG-PLGA repeat units: EG-LA/GA = 106-75/80 M_N = 4670-5367/4639, LA/GA ratio = 54%/46%

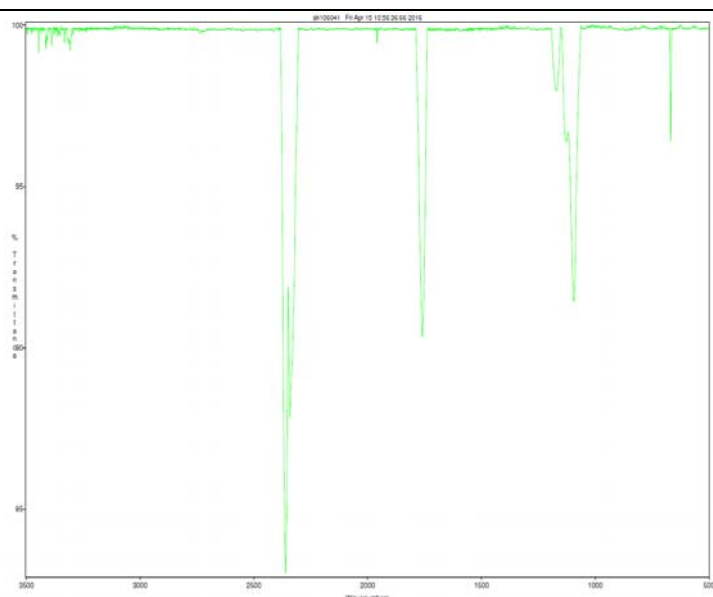

FTIR Analysis: Collected from cast-film on KBr salt-plate placed in Satellite FTIR (Thermo-Mattson) and analyzed in transmission mode.

• GPC analysis of mPEG-PLGA copolymers

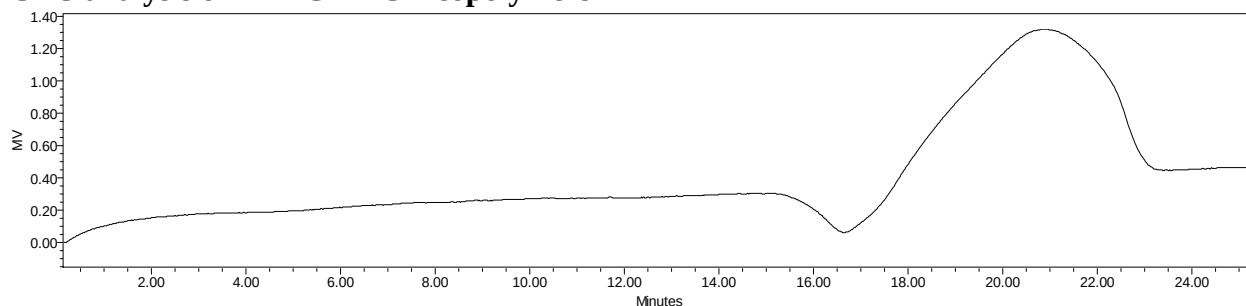


Analysis Method: Waters Breeze 2 system with 1 ml/min DCM flow across three Phenogel 5um columns (Phenomenex). Detection via refractive index, calibrated against polystyrene standards.

Polymer	Mn (from GPC)	Mw (from GPC)	PDI
mPEG-PLGA	11,586	20,609	1.78
mPEG5000 initiator*	4,677	5,272	1.13

*calibrated against PEG standards

• Structure of mPEG-PLGA copolymers

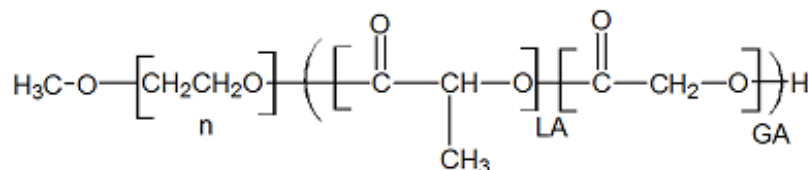

Material provided for research use only. Not for human use.

PolySciTech Division of Akina, Inc. | 3495 Kent Avenue, West Lafayette, IN 47906

765-464-0390 | www.polysciotech.com

For research use only.