
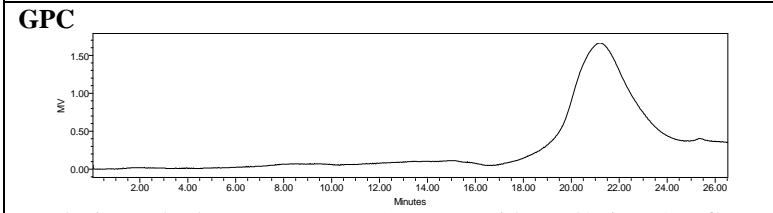
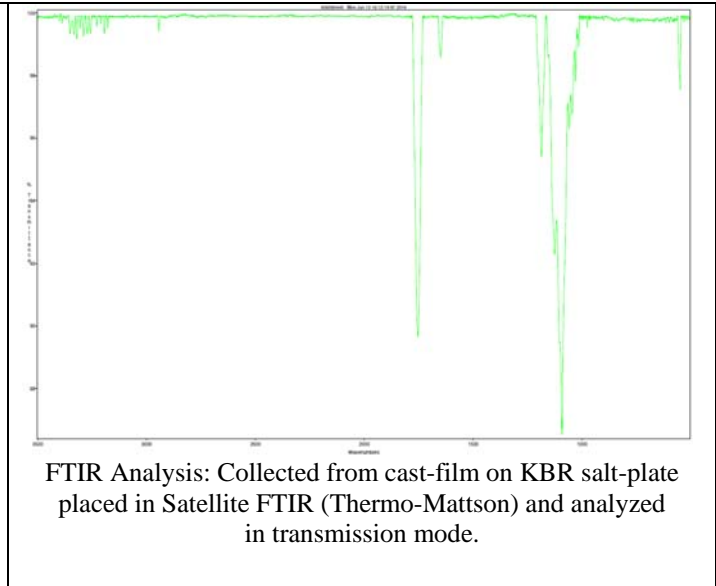


# No. AK119 Certificate of Analysis

Product Name: Poly(lactic-co-glycolic acid)-*b*-Poly(ethylene glycol)-*b*-Poly(lactic-co-glycolic acid) copolymers (Mw~1,000:1,000:1,000 Da, LA:GA 15:1) (Lot# 60608MMH-B)

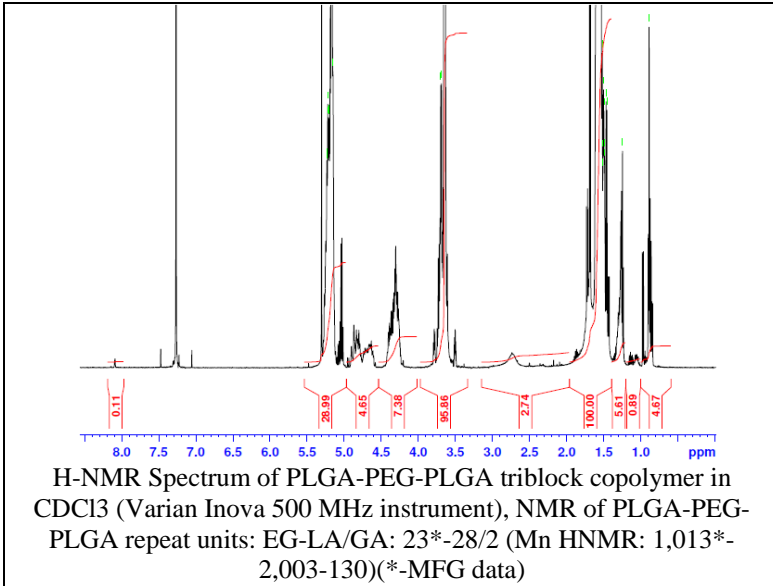


Analysis Method: Waters Breeze 2 system with 1 ml/min DCM flow across three 300x7.6 mm GPC columns (mixed porosities). Detection via refractive index, calibrated against polystyrene standards.

Polymer	Mn (GPC)	Mw (GPC)	PDI
PLGA-PEG-PLGA	4,037	7,294	1.81
PEG precursor	Manufacturer Nominal – 950-1,050*		


\*- MFG provided data.

**Rheology**  
 Rheology performed on AR550 (TA instruments) with 60mm 2degree cone on 20% w/v polymer in distilled water dissolved over 2 days with shaking at 4C. Viscosity of solution at 0.1 (sec-1) and 5C was measured (1minute peak hold 5 second test intervals). Rheology performed by oscillating at constant 6.283 rad/s, 0.1% strain, in increments of 2.5C ranging from 5-45C with 3 minutes of temperature equilibration at each point.

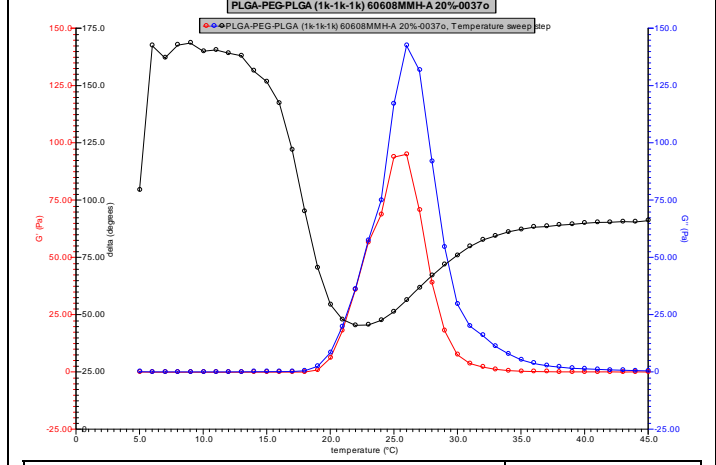

Viscosity 20% w/v solution at 5C | 0.0727 Pa.s

• **Structure of PLGA-PEG-PLGA copolymer**

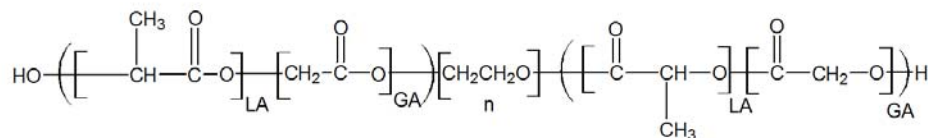

Material provided for research use only. Not for human use.