


# No. AK152


# Certificate of Analysis




Product Name: Poly(lactide-co-glycolide)-b-Poly(ethylene glycol)-b-Poly(lactide-co-glycolide) 1200-1500-1200Da (LA:GA 15:1 (94%/6% LA/GA) (w:w))  
Lot #190911RAI-B

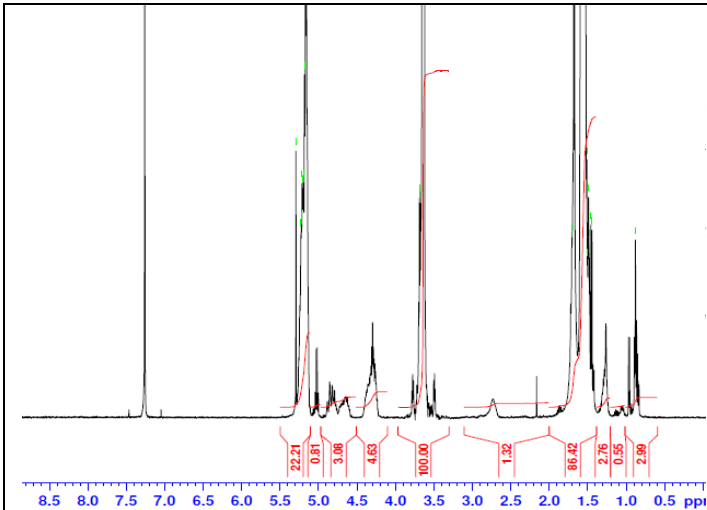

H-NMR Spectrum of copolymers in CDCl<sub>3</sub> (Bruker 500 MHz, PINMRF) NMR of PLGA-PEG-PLGA copolymer: EG/LA-GA =34/30-2 (Mn EG/LA:GA 1498\*/2175:121 Da)

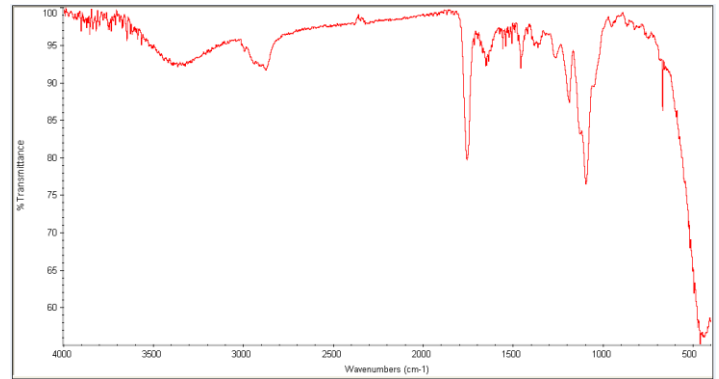


FTIR Analysis: Collected from cast-film on KBr salt-plate placed in Nicolet Avatar 320 spectrometer and analyzed in transmission mode.

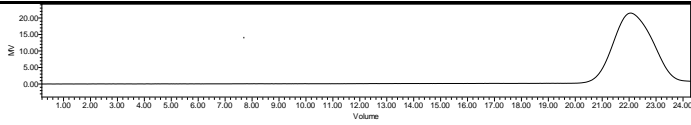

GPC Analysis Method: Waters Breeze 2 system with 1 ml/min THF flow across three GPC columns. Detection via refractive index, calibrated against polystyrene standards.

Polymer	M <sub>n</sub> (from GPC)	M <sub>w</sub> (from GPC)	PDI
PLGA-PEG-PLGA	4724	5702	1.21
PEG precursor*	1484*		

\*- from MFG data

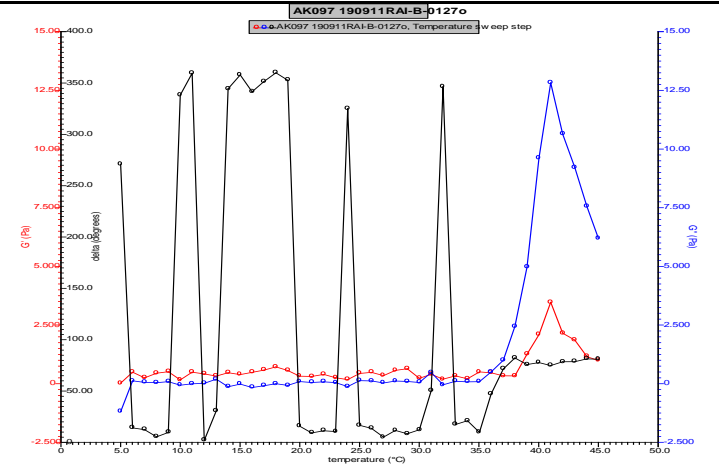

Rheology performed on AR2000 (TA instruments) with 60mm 2degree cone on 20% w/v polymer in water dissolved over 3 days with stirring at 4°C. Viscosity of solution at 0.1 (sec<sup>-1</sup>) and 5°C was measured (1minute peak hold 5 second test intervals). Rheology performed by oscillating at constant 6.283 rad/s, 0.1% strain, in increments of 1°C ranging from 5-45°C with 1 minutes of temperature equilibration at each point.

Viscosity 20% w/v solution at 5°C | 0.01438 Pa-s

## Structure of PLGA-PEG-PLGA

