


No. AP081

Certificate of Analysis




Product Name: Poly(lactide-co-glycolide) acid endcap (50:50 LA:GA) (Mn: 5,000-10,000 Da)
(Lot#: 250715DJR-B)

H-NMR

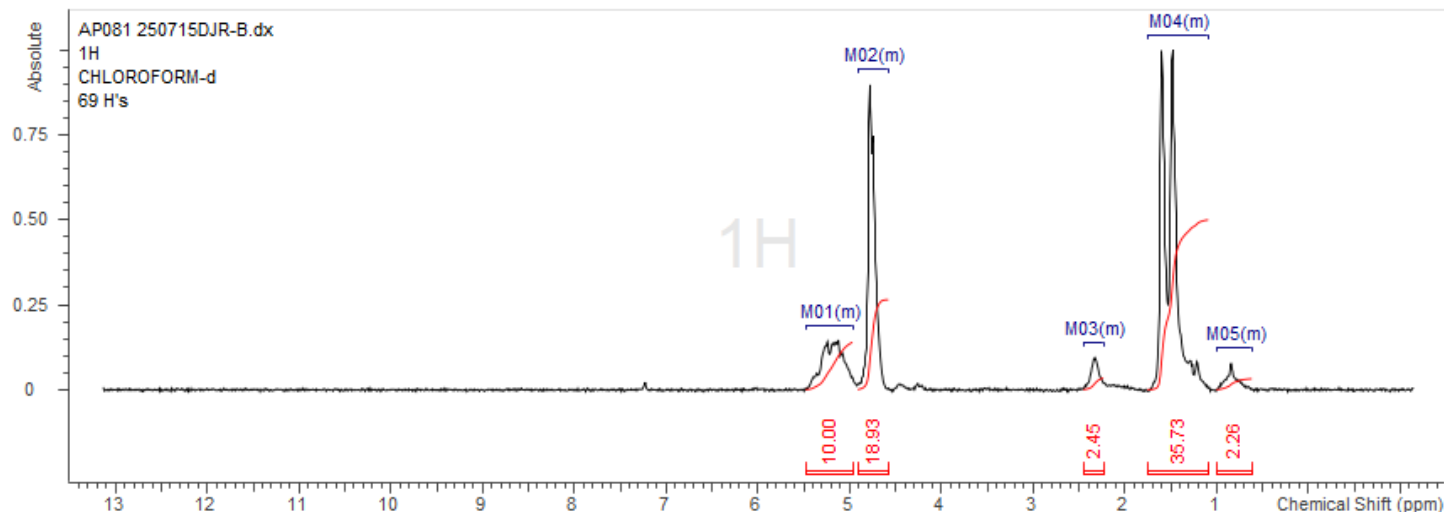


H-NMR Spectrum of copolymers in CDCl₃ (NMReady-60e, Nanalysis 60 MHz) NMR of PLGA copolymer: LA-GA =51%-49% molar ratio (LA:GA 57%:43% w:w)

FTIR

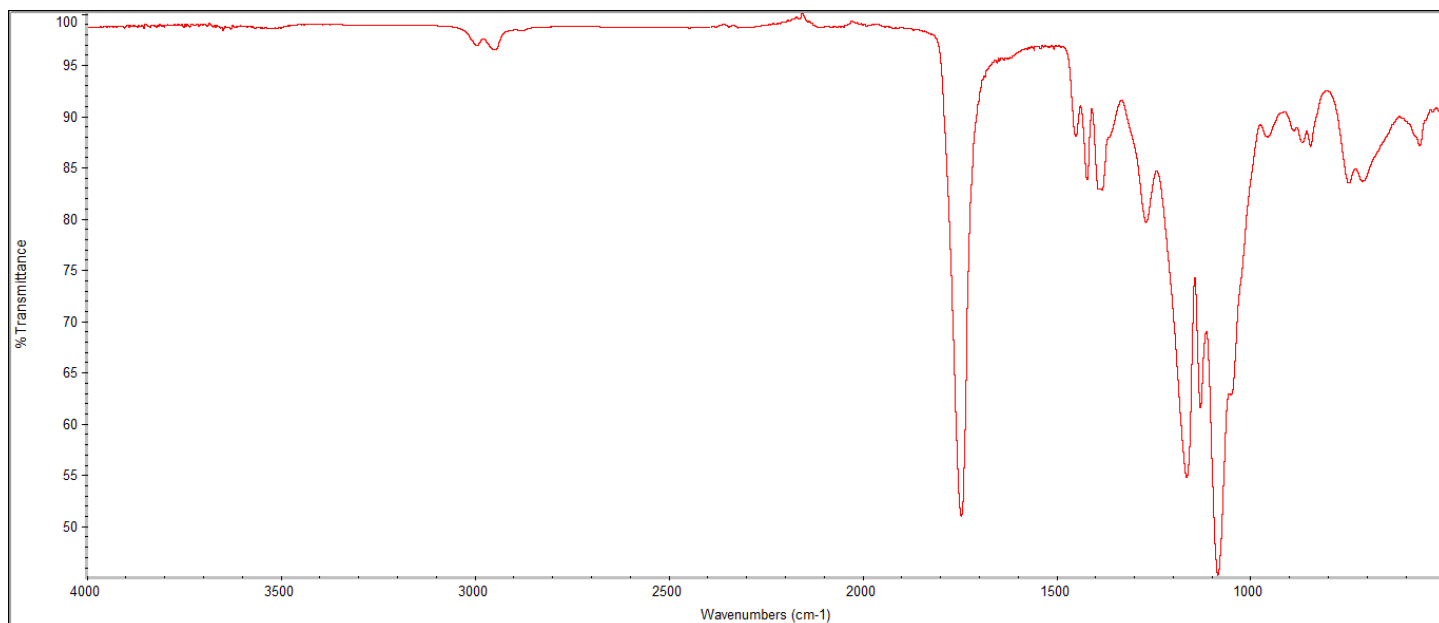

FTIR Analysis: Collected from IS5 ID7-ATR spectrometer (Thermo Scientific) and analyzed in transmission mode.

GPC-ES

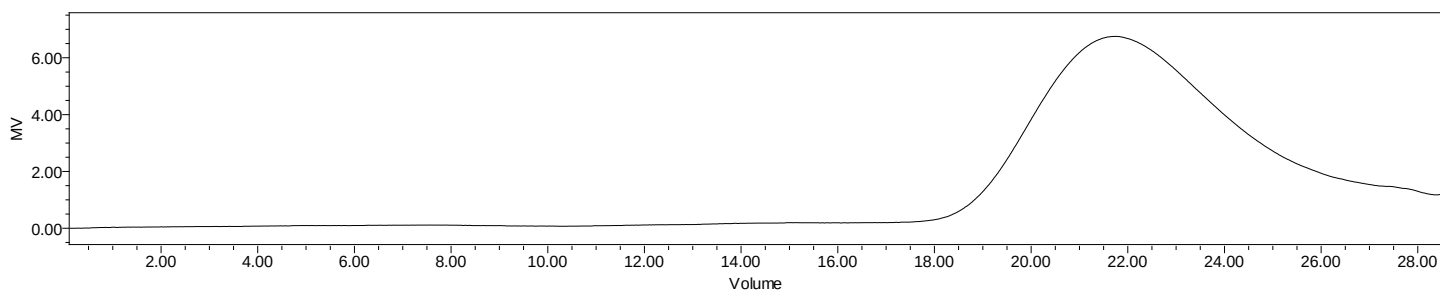

Polymer	M _n (from GPC)	M _w (from GPC)	PDI
PLGA	6172	11,255	1.82

GPC-ES Analysis Method: Waters Breeze 2 system with 1 ml/min THF flow across three GPC columns. Detection via refractive index, calibrated against polystyrene standards.


DSC

Sample: AP081 250715DJR-B
Size: 4.0000 mg
Method: Ramp

DSC

File: C:\...\COA\AP081 250715DJR-B DSC.001

Run Date: 24-Jul-2025 13:11
Instrument: DSC Q2000 V24.11 Build 124

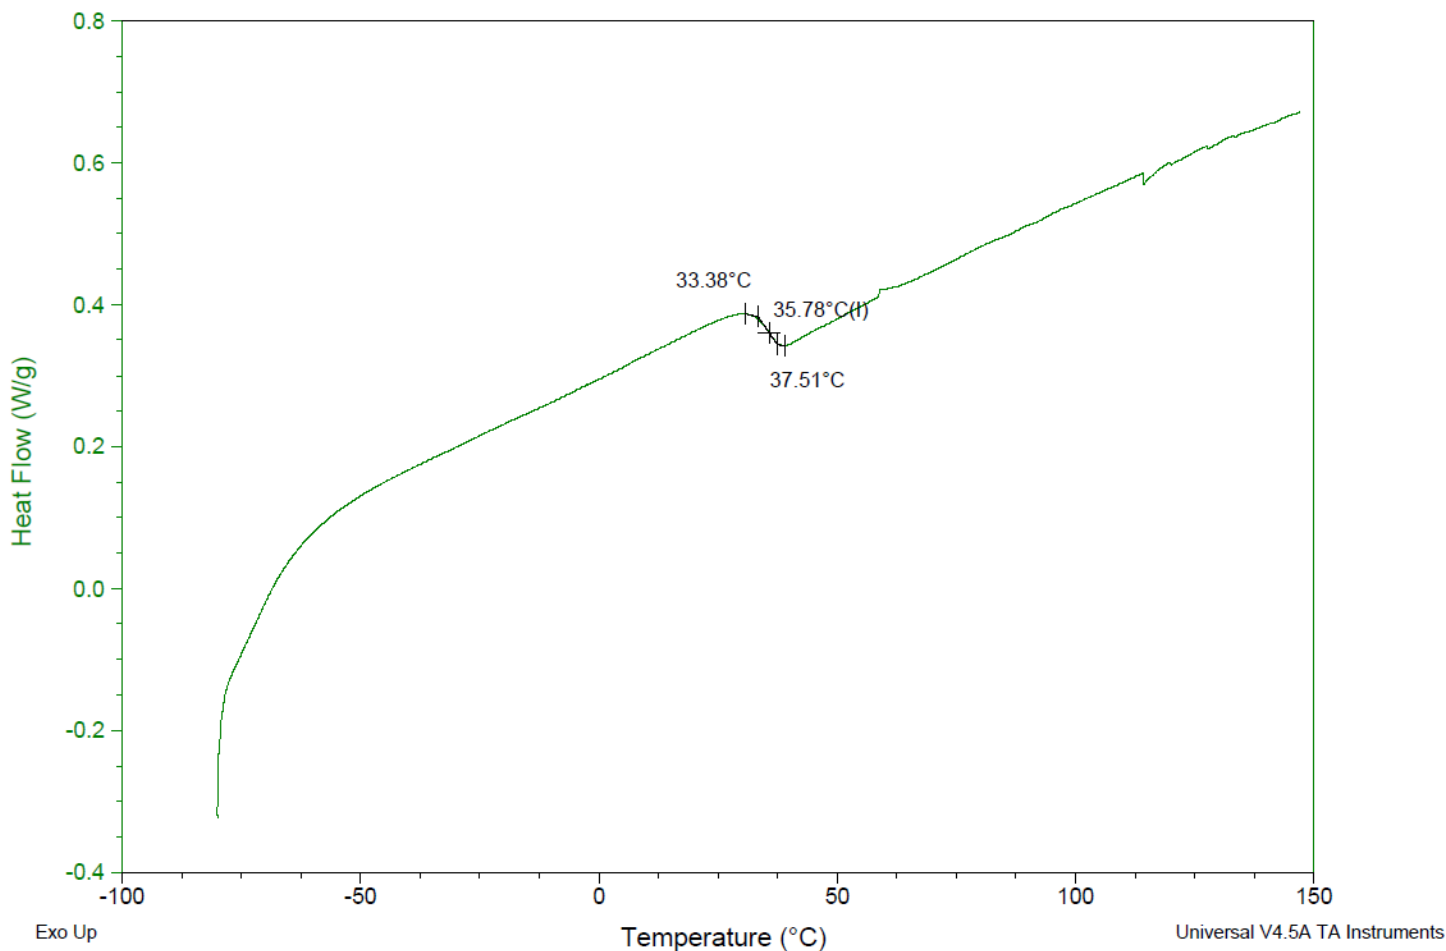


DSC Testing: 1-5 mg sample tested in crimped aluminum pan on a TA Instruments Model Q2000 with procedure equilibraion 100 °C, isothermal 5 minutes, equilibrate -80 °C, data on, ramp 10 °C/min to 150 °C. Tg = 35.78 °C

IV

Inherent Viscosity: 0.133 ± 0.006 dL/g (calculated from kinematic viscosity at 2% w/v Acetone on Rheosense microVISC, n=3) at 25°C.

Structure of copolymers

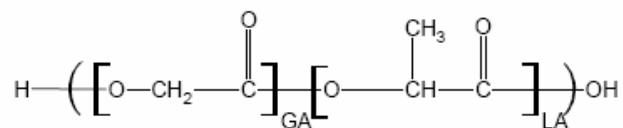

Approved By:
Amie Tyler
Quality Manager